

de Havilland

Material Specification

TITLE:	FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INERIOR USE)
SPECIFICATION NUMBER:	DHMS P 1.40
ISSUE:	E
AMENDMENT:	1
DATE:	April 21, 2017
PAGE:	1 of 19

Information in this document is **proprietary** to Bombardier de Havilland. This document must not be reproduced or distributed in the whole or in part to a third party without prior express permission in writing from de Havilland.

Prepared by:

Approved by:

SIGNED ORIGINAL ON FILE

Hai Yen Tran

Materials Technology

Bruce Campbell

Manager, Q400 Product Development

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E AMD.: 1
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	DATE: April 21, 2017 PAGE: i of ii

REVISION RECORD

Issue	Page	Description and Reason for Change
A		This is a complete revision and detail changes have not been noted.
		Gel time and% Resin Flow specification are added to QPL.
Amd. 1	QPL	CYTEC was added to QPL
B		This is complete revised issue. Detail changes have not been noted.
Amd. 1	QPL	Requirement of Resin flow for Cytec, supplier of Type 3 material changes from 33±6% to 20-33%.
Amd. 2	4-6	Resin Content test method has been changed.
Amd. 3	7	Figure 1 has been changed.
	10	Flammability specimen has been added in Table 4.
Amd. 4	17	QPL: Cytec has been deleted from QPL.
Amd. 5	17	QPL: Addresses have been added for Culver City Composites.
C	QPL	JD.Lincoln Product L-756FR-285K has been added to QPL
		Culver city product CE9010A/K285 has been requalified at new manufacture site Anaheim. Product designation and address has been changed.
	4	Storage Life definition has been changed.
	6	Flexural test specimen's dimension changed to 3" x 1", test at L/D=16 (standardize with DHMS P1.24)
	9	Table 3, Flexural Strength test at 300°F.
C	6	Specified Flex test with support span of 2", load span of 0.67"
Amd. 1		Shear test with crosshead speed of 0.05"/min., support span of 0.50".

de Havilland	DHMS: P 1.40 ISSUE: E AMD.: 1 DATE: April 21, 2017 PAGE: ii of ii
Material Specification FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

REVISION RECORD

Issue	Page	Description and Reason for Change
D		This is a complete revision and detail changes have not been noted.
	2	Replaced ASTM D 720 with ASTM D6272
	6	Reword Tack test, Marking.
	6	Temperature and Humidity for testing changed to 70°F ± 10°F maximum 60%
	7	Clarified Flex test is 4 point bend. ASTM D6272, Short Beam Shear Test, added span requirement for thickness larger than 0.130"
	10	Table 3. Corrected the Short Beam Shear Strength requirement. Was: 1500 psi, Now: 4000 psi
	13-18	Updated section 5, 6, 7,8 standardize with other specifications
	19	QPL, added Cytec Winona site for product L-756FR/285K Deleted Cycom 9010A/K285 as product no longer available.
Amd. 1	17	8.2.1 Clarified the non-adherent film on the outside.
E		3.3 Defect: Max defect allowable 5%.
		3.4.2 Working Life: Maximum humidity of 60%
		3.4.3 Formability: Clarified temperature and humidity
	6	3.4.8 Tack: Maximum humidity of 60% 3.4.10 Marking: Added example of marking 3.4.12 Reword Workmanship.
	15	Table 6, Revised acceptance test requirements for both Supplier and Purchaser/ User.
	19	QPL: Cytec name changed to Cytec Solvay Group
		QPL: Remove J.D.Lincoln manufacturing site Table 6. Added Flammability test requirement as acceptance test.
Amd. 1	19	

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
		DATE: August 2, 2016
		PAGE: 2 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)		

1 SCOPE

This specification establishes the requirements for a 350°F cure epoxy resin impregnated, aramid fabric, supplied in a "B" stage condition, suitable for autoclave pressure laminating of interior composite panels.

1.1 Classification

The materials supplied to this specification shall be furnished in the following Classes and Types:

Class 2 - Non self-bonding, requiring an approved film adhesive for use with honeycomb core material.

TABLE 1. Classification

Type	Style	Resin Content	Cured Ply Thickness (Nominal)
3	285	47 - 55%	0.011"

2 APPLICABLE DOCUMENTS

The following documents form a part of this specification to the extent defined herein. In the event of conflicting requirements between this and the specifications listed below, the requirements of this specification shall govern. Where a specific issue of a document is not specified, the current issue shall be used.

2.1 U.S. Government Specifications

2.1.1 Federal aviation Administration

FAR 25.853 (a), APP. F, - Flammability requirements

Part I (1) (i)

Advisory Circular 21-26 - Quality Control for the Manufacture of Composite Structures

2.2 American National Standard Institute

ANSI B46.1-78 - Surface Texture

2.3 American Society for Testing and Materials

ASTM C613 - Resin Content of Carbon and Graphite by Solvent Extraction.

ASTM D6272 - Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials by Four-Point Bending

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
		DATE: August 2, 2016
		PAGE: 3 of 19

- | | |
|------------|--|
| ASTM D2344 | - Apparent Horizontal Shear Strength of Reinforced Plastics by Short Beam Method |
| ASTM D3039 | - Tensile Properties of Oriented Fiber Composites |
| ASTM D3410 | - Compressive Properties of Unidirectional or Crossply Fiber Resin Composites |

2.4 de Havilland Inc. Specifications & Standards

- | | |
|------------|--|
| DHMS A6.09 | - High Temperature Epoxy Adhesive/Liquid Shim Material |
| DSC 234 | - Composites Manufacture Expendable Materials |

2.5 Aerospace Material Specifications

- | | |
|----------|--|
| AMS 3901 | - Organic Fiber, Yarn and Roving, High Modulus for Structural Composites |
| AMS 3902 | - Fabric, Organic Fiber, High Modulus for Structural Composites |
| AMS 3903 | - Fabric, Organic Fiber, High Modulus, Epoxy Resin Impregnated |

3 REQUIREMENTS

3.1 Fabric

The aramid fiber fabric, Type 3 shall meet all the requirements of AMS 3902. See [Table 2](#) for the make-up of fabric.

3.1.1 Ends - The fabric shall not contain any unspliced yarns or tow ends.

3.1.2 Fabric, Unimpregnated Weight - The basic weight of the fabric shall meet the requirements given in [Table 2](#). For acceptance test, the weight of the fabric shall be determined as per para. 3.4.5.

TABLE 2. Unimpregnated Fabric

Type	Style	Construction Ends/Inch (Denier)	Weave	Basic Weight oz/sq.yd.	Thickness Inches (Nominal)
3	285	17(1140)x17(1140)	Crowfoot	5.0 ± 0.30	0.010"

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E AMD.: -- DATE: August 2, 2016 PAGE: 4 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

3.2 Preimpregnated, Aramid Fiber Fabric

The product shall be the fabric noted in [Para.3.1](#) of this specification, impregnated with an epoxy resin system, supplied in the "B" stage condition, and shall be formulated to meet the requirements specified herein.

3.3 Defects

Materials may not contain defects in excess of totalling more than 5% of the area of the complete roll. Defects shall be flagged by placing a strip of polyethylene backing, or other identifying material, at the location of the defect and extending it out one or both ends of the roll. Additional material may be added to the roll to compensate for all defect areas occurring in the roll or supplier will deduct the defect length from the roll length sold to the customer. Compensating material shall be the full roll width for each length of affected area. Alternatively, the purchase liability shall be reduced equal to the amount of compensating material otherwise due.

3.4 Physical Properties of Uncured Impregnated Fabric

Tests shall be performed on the product as received, after warming to above the dew point to sampling and in accordance with the test methods specified herein.

3.4.1 Storage Life - The storage life shall be a minimum 180 days from the date of shipment, 270 days from the date of manufacture, when stored at a temperature of 0°F or below.

3.4.2 Working Life - The product shall meet the requirements of this specification when tested after exposure to a temperature not greater than 77°F, with a humidity not greater than 60%, for a continuous period of up to 7 days.

3.4.3 Formability - Formability is defined as the ability of the product to be deformed or contoured over a mould during normal fabrication processes at a temperature range of 65-77°F with maximum humidity of 60% and be cured in that position. The product shall be formable over, or into, a 0.15 inch minimum radius and remain in position throughout fabrication. Heat may be applied locally to aid in achieving this requirement.

3.4.4 Volatile Content - Three 4 inch x 4 inch specimens of the uncured material shall be weighed individually on an analytical balance to the nearest 10 mg and placed in an air circulating type oven at 325 ± 10 °F for 15 minutes. The specimens shall be removed from the oven, placed in a desiccator, cooled to room temperature and reweighed, in order to calculate the volatile content.

$$\text{Volatile Content, \% by weight} = \frac{W1 - W2}{W1} \times 100$$

W1 = Original Weight

W2 = Weight After Heating Cycle

The volatile content, by weight, shall not be greater than 2%.

3.4.5 Resin Content by Weight/ Fabric Weight - The resin content by weight shall be calculated and recorded and shall meet the requirements of [Table 1](#). Three specimens, approximately 4" x 4" each, shall be cut from the roll so that one sample comes from the centre of the width and the other two from the edges.

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E AMD.: -- DATE: August 2, 2016 PAGE: 5 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

Note: volatile content must be performed on different samples.

The three samples shall be individually weighed on an analytical balance and weights recorded to the nearest 10 mg. Completely submerge the three samples in separate beakers containing a minimum of 50 ml Methyl Ethyl Ketone, Acetone, or Methylene Chloride for at least 5 minutes. Decant the solvent, being careful to retain all fibers and replace with clean solvent. Continue to extract and decant the sample for a minimum of 3 extractions, until all traces of resin have been removed. Dry the fibers at 210° ± 10° F for 15 minutes. The specimens shall then be cooled to room temperature in a desiccator, reweighed, and the resin content /fabric weight calculated as follows:

$$\text{Resin Content, \% by weight} = \frac{W1 - W2}{W1} \times 100$$

Fabric Weight = $W2$

$W1$ = Original Weight

$W2$ = Weight After Extraction

- 3.4.6 Resin Flow by Weight - Three specimens, each one 4" x 4" x 4 plies, of the uncured material shall be laid up cross plied (90° to each other) and weighed on an analytical balance to the nearest 10 mg. The specimens shall then be positioned between 0.0015" aluminum foil which is coated with release agent and placed individually in a press, preheated to 325 ± 10 °F at 50 ± 5 psi pressure and cured for 15 minutes. Remove the specimen and allow to cool. The foil shall be removed, the flash broken off and each specimen individually reweighed to the nearest 10 mg. The average flow rate of the three specimens shall be calculated by the weight difference between the uncured and cured specimen, multiplied by 100 and divided by the uncured weight.

The resin flow shall be as specified on the Qualified Products List of this specification.

3.4.7 Gel Time

Method 1

Three specimens, each being approximately 1/4" square, shall be cut from the uncured material. A hot plate shall be preheated to 325° ± 10° F, unless otherwise specified, and a micro cover glass placed on the hot plate, allowing a minimum of 20 seconds for it to reach equilibrium. One specimen shall be placed at the centre of the micro cover glass and timing shall be commenced. Within 5 seconds, a second micro cover glass shall be placed over the specimen. When the resin softens during the first 30 seconds, the top micro cover glass shall be probed to isolate a drop of resin. The fluidity and colour of the isolated drop shall be observed periodically at first, and continuously as the end point approaches. The lateral spreading movement of the resin, upon probing, will decrease and the colour will change as the gel point approaches. The timer shall be stopped at the first indication of resin immobility and the elapsed time to the nearest minute shall be recorded.

Method 2

- Apparatus:
1. Fisher-Johns melting point apparatus
 2. Thickness No.2 18 mm cover glasses
 3. Timer or stopwatch
 4. Wooden picks or equivalent.

- Procedure:
1. Preset the Fisher-Johns melting point apparatus to read 325° ± 10° F of the

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	AMD.: -- DATE: August 2, 2016 PAGE: 6 of 19

specified temperature.

2. Insert a 1/4" x 1/4" sample between 2 cover glasses and place on the Fisher-Johns apparatus.
3. Start the timer and probe the specimen with a wooden pick.
4. When resin gels (this is usually evident when no resin movement is seen when moderate pressure is applied to the specimen), stop the timer and report the gel time to the nearest 0.1 minute.

The product shall have a gel time at 325° F, as shown on the Qualified Products List of this specification, unless otherwise specified.

3.4.8 **Tack** - The product shall exhibit a degree of tackiness to enable easy handling during normal fabrication processes at a temperature range of 65- 77°F, with a humidity not greater than 60% anytime during the defined shelf life. Both sides of the fabric shall exhibit a degree of tackiness so that the fabric, when folded 180°, will adhere lightly to itself. It shall also be capable of being removed, after light hand pressure during lay-up, without disturbing the previously positioned mating ply.

3.4.9 **Colour** - For all products, the material shall be supplied in the natural colour of the resin fiber system.

3.4.10 **Marking** - The warp direction of the woven impregnated fabric shall be marked in a manner that is acceptable to Materials Technology, de Havilland. The warp face of the impregnated fabric shall be against the separator film. Acceptable methods include but are not limited to ink arrows, ink lines, incorporated tracer yarns

3.4.11 **Dimensions**

Width - Unless otherwise specified, the overall width of the product, shall be 38" or 50" inclusive of the selvage for Type 3. Width tolerance shall be ± 0.50 inch.

Length - Unless otherwise specified, the overall length of the product, shall be 25 \pm 1 yard, 50, 100 or 150 yards \pm 5 yards.

3.4.12 **Workmanship** - The impregnated aramid fabric shall be evenly impregnated, uniform in quality, and free from gaps, holes, resin pockets, cured resin particles, foreign materials, creases and other similar defects which will render the product unsuitable for its intended purpose.

3.4.13 **Bias or Bowed Filling** - The filling strands of Type 3 shall not be distorted from the horizontal by more than 3" for 38" width and proportionately for all other widths.

3.5 Mechanical Properties and Test Methods of Cured Impregnated Fabric

3.5.1 Unless otherwise specified, tests shall be conducted at 70°F \pm 10°F and a relative humidity of maximum 60%. Specimens tested at room temperature shall be conditioned for a minimum of 24 hours at 70 \pm 10°F and maximum 60% relative humidity immediately prior to the test. At least five specimens shall be used per test except for flammability test which requires a minimum of three specimens, and the results averaged. No individual value shall be less than 90% of the value specified; this shall not apply to flammability tests.

Unless otherwise specified, all test pieces shall be cut with the longer dimension parallel to the warp direction of the fabric

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E AMD.: -- DATE: August 2, 2016 PAGE: 7 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

3.5.2 Flammability -

For Types 3, a two ply cured laminate fabricated per [Para.4.1](#), shall meet the requirements of FAR 25.853(a) APP. F, Part I(a)(1)(i).

3.6 **Laminate Mechanical Properties**

3.6.1 Tensile Tests - The ultimate tensile strength and the tensile modulus of each specimen shall be calculated and recorded and shall be not less than values given in [Table 3](#). For Type 3, five tensile test specimens shall be tested in accordance with ASTM D3039 with a cross head speed of 0.05"/min except that the specimens shall conform to [Figure 1](#).

3.6.2 Flexural Tests - The flexural strength (modulus of rupture) and flexural modulus (tangent modulus of elasticity) shall be calculated and recorded and shall be not less than the values given in [Table 3](#). Five flexural specimens, 3" warp x 1" fill, with the long dimension parallel to the warp direction shall be tested in accordance with ASTM D6272, 4pt. bend and test with a crosshead speed of 0.06"/minute, support span of 2", load span of 0.67". Test with load applied at the tool side (smooth side) of the specimen.

3.6.3 Compressive Tests - The ultimate compressive strength of each specimen shall be not less than the value given in [Table 3](#). Five specimens conform to [Figure 2](#) shall be tested in accordance with ASTM D3410.


3.6.4 Horizontal Shear Strength Test - The Horizontal Shear strength shall be calculated and recorded and shall be not less than the value given in [Table 3](#). Five test specimens 1.125" long (parallel to fill) by 0.25" wide (parallel to warp), for Type 3 material and shall be tested in according to ASTM D2344 with a crosshead speed of 0.05"/minute and a support span as follows:

0.50" - for specimen thicknesses up to 0.130";

0.65" - for specimen thicknesses greater than 0.130".

Test with load applied at the tool side (smooth side) of the specimens.

<div>de Havilland</div> <div>Material Specification</div>	<div>DHMS: P 1.40</div> <div>ISSUE: E</div> <div>AMD.: --</div> <div>DATE: August 2, 2016</div> <div>PAGE: 8 of 19</div>
<div>FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)</div>	

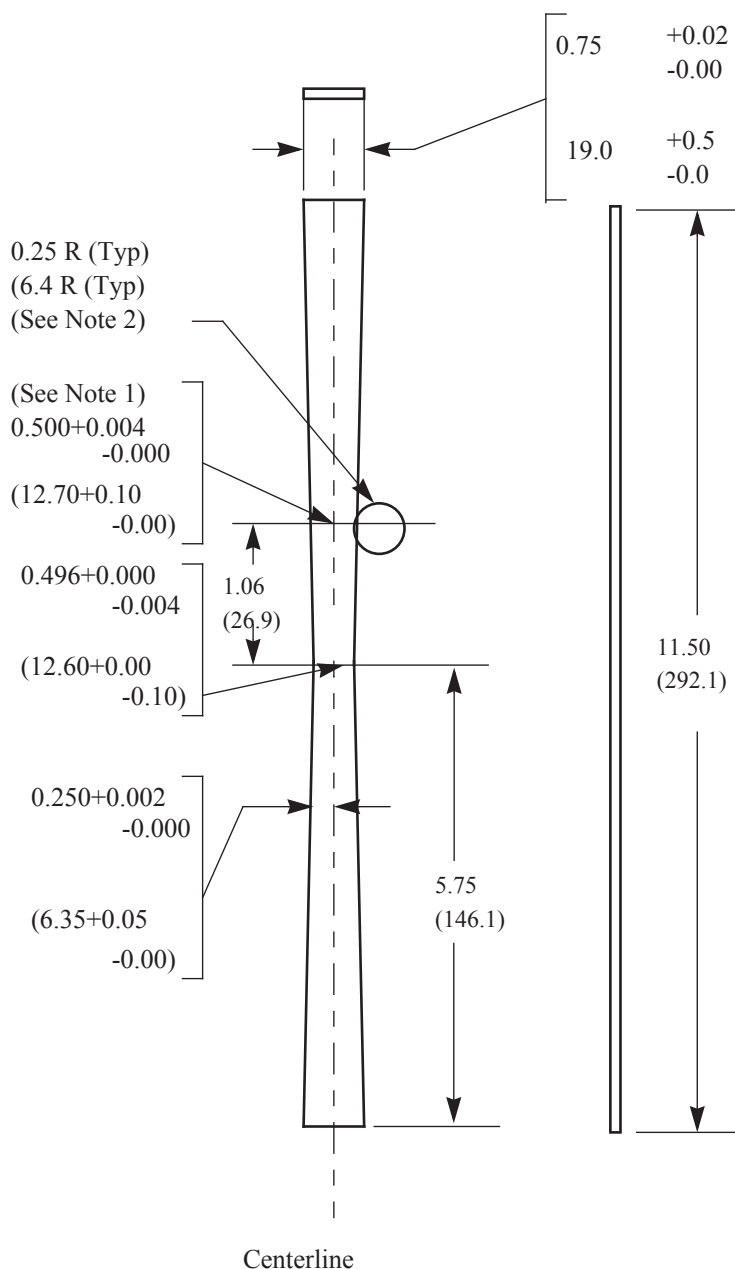

Dimensions are in inches and millimeters.

Notes:

1. The width outward from 0.496 (12.60) shall be increased gradually and equally on each side up to 0.500 (12.70) so that no abrupt change in dimensions results.

2. Transition from straight sided center section to tapered section shall be smoothly joined in the area of the 0.250 (6.35) rad.

3. Test at crosshead speed of 0.15"/min.

FIGURE 1. TENSILE STRENGTH SPECIMEN

de Havilland	DHMS: P 1.40 ISSUE: E AMD.: -- DATE: August 2, 2016 PAGE: 9 of 19
Material Specification FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

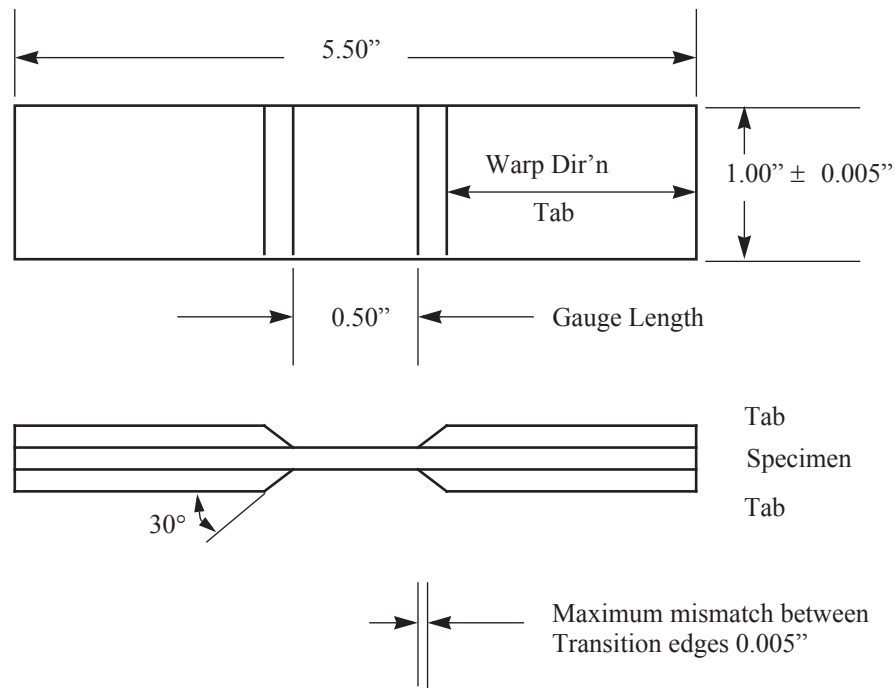


FIGURE 2. COMPRESSIVE TEST SPECIMEN

Notes:

1. Specimen thickness shall be 10 plies.
2. Tabs to be manufactured from 10 plies DHMS P1.40 Type 1 glass fabric and cured at $260 \pm 10^\circ \text{ F}$, $35 \pm 5 \text{ psi}$ for one hour.
3. Use Frekote 44NC or 700NC on caul plate (0.032 - 0.060 thick) on upper surface. Do not use Tooltec.
4. Tab face which is to be bonded to specimen shall be cured with peel ply to DSC-234 12 to provide adequate bond surface.
5. Tab thickness is 0.100 ± 0.010 " but all 4 tabs on a specimen must be within 0.002" of each other.
6. Maximum mismatch between tab transition edges is 0.005".
7. Tab lay up may be done in panels and cut to size; no tab may be cut from material within 1/2 inch of the edge of the panel. Bond surface is surface which was cured with peel ply on it.
8. Bond tabs to specimen using 3M, 2 part adhesive EC 2216 or DHMS A6.09 liquid shim. Lightly abrade specimen surface (320 grit abrasive) only where tabs are to be bonded on. Use a fixture to maintain warp direction of tab during lay up. Peel ply must be removed from tab before bonding commences. Wipe bond surfaces with MEK immediately before bonding.
9. 125√ edge finish is required in accordance with ANSI B46.1-78.

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
		DATE: August 2, 2016
		PAGE: 10 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)		

TABLE 3. Laminate Mechanical Properties

Test	Reference	Minimum Average Values (psi)
		Type 3
Tensile Strength	ASTM D3039	50,000
Tensile Modulus	ASTM D3039	3.0 x 10 ⁶
Flexural Strength at 75° F	ASTM D790	40,000
Flexural Strength at 300° F	ASTM D790	24,000
Flexural Modulus	ASTM D790	3.0 x 10 ⁶
Compressive Strength at 75° F	ASTM D3410	20,000
Short Beam Shear Strength at 75° F	ASTM D2344	4000

4 TEST PANEL FABRICATION


4.1 Laminate Specimen

Test laminate 18" warp x 12" fill shall lay up with number of plies specified in [Table 4](#) with the long dimension parallel to the warp direction. Laminate shall be vacuum bagged per the applicable [Figure 3](#) and cured per [Figure 4](#).

TABLE 4.

Test Specimen	# Plies for Type 3
Flexural	10
Horizontal Shear	10
Tensile	10
Compression	10
Flammability	2

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E AMD.: -- DATE: August 2, 2016 PAGE: 11 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	

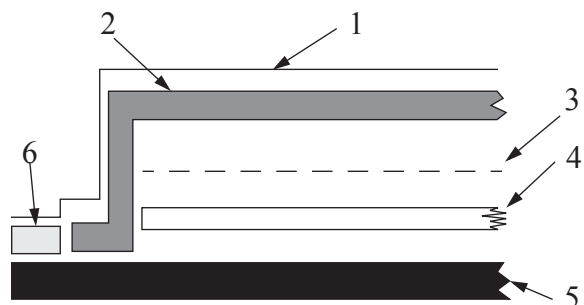

Use DSC 234 expendable materials

1. Nylon Vacuum Bag
2. Airweave SS-FR Breather
3. Perforated Release Film A4000P3
4. PART
5. Tool (coated with mould release Frekote 44 NC or 700NC)
6. GS 43 MR Vacuum Sealant Tape

FIGURE 3. BAGGING PROCEDURE FOR TYPE 3 LAMINATE AND SANDWICH PANELS

APPROVED EXPENDABLE MATERIALS TO DSC 234

Wrightlon 8400	(DSC 234-2-54)	Airtech International Inc., 2542 East Del Amo Blvd., P.O. Box 6207 Carson, CA 90749 (213) 603-9683
Perforated Release Film A4000P3	(DSC 234-5-48)	
Airweave SS-FR Breather	(DSC 234-11)	
Mould Release, Frekote 44NC or 700NC	(DSC 234-13-3/4)	Frekote Inc., 170 W. Spanish River Blvd., Boca Raton, FL 33431 (305) 395-3082
Vacuum Sealant Tape, GS 43 MR	(DSC 234-17-1)	

Note: Additional sources are listed in DSC 234.

<div>de Havilland</div> <div>Material Specification</div>	<div>DHMS: P 1.40</div> <div>ISSUE: E</div> <div>AMD.: --</div> <div>DATE: August 2, 2016</div> <div>PAGE: 12 of 19</div>
<div>FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE</div> <div>EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)</div>	

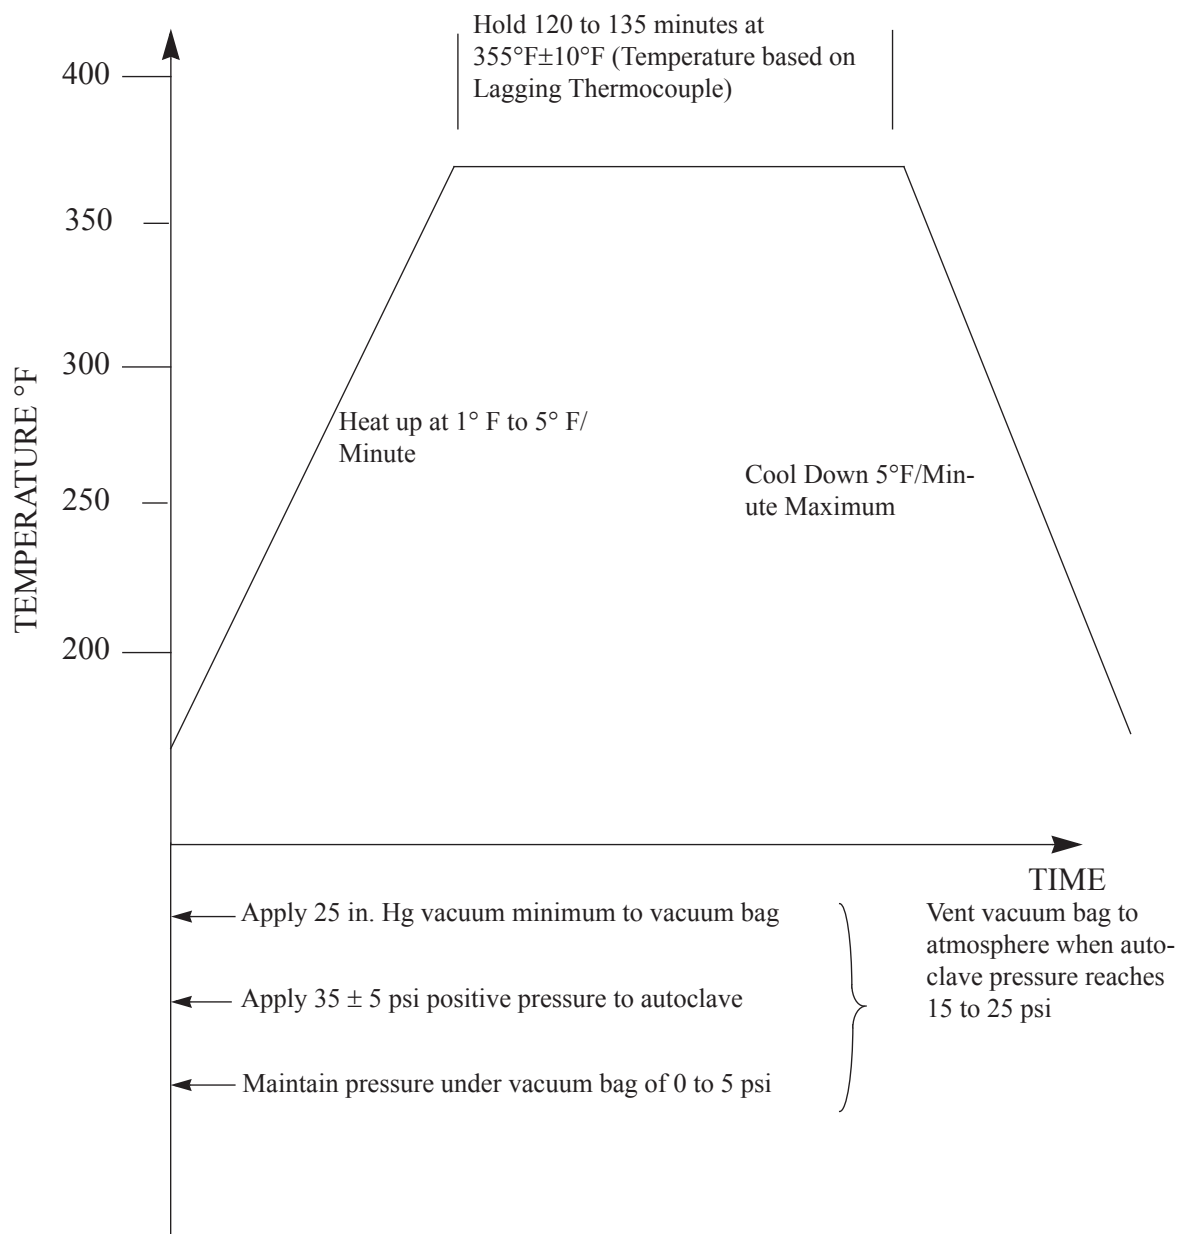


FIGURE 4. Cure Cycle for Type 3

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
		DATE: August 2, 2016
		PAGE: 13 of 19

5 MATERIAL QUALIFICATION REQUIREMENTS

5.1 Request For Qualification

All requests for qualification to this specification shall be addressed to Bombardier Aerospace Materials Technology Engineering department for approval.

All material qualification shall be site specific.

An audit of the manufacturers and/or test facilities by Materials Technology Engineering may be necessary prior to approval.

5.2 Qualification testing

Potential suppliers shall submit a written qualification test report based on 3 batches/lots of materials showing compliance with the requirements contained in section 3. The test report shall contain actual numerical test values, average test results as well as failure modes where applicable.

5.2.1 A sample shall be submitted for testing at the discretion of Bombardier Aerospace Materials Technology for evaluation.

5.3 Qualification by Similarity

Where a product has been qualified to another similar specification, the supplier may submit the qualification data applicable to this specification for consideration. The similar specification may be a government, company, or other aerospace specifications where the requirements are similar to this specification.

5.4 Process Control Document

5.4.1 The manufacturer shall develop and maintain a Process Control Document (PCD).

5.4.2 The PCD shall define the manufacturing and quality control requirements and procedures for assuring consistent, uniform and compliant products. The PCD shall identify baseline chemical constituents, in-process test procedures and requirements, and manufacturing procedures. All specifications and test procedures employed during the process shall also be listed and issue/date controlled.

5.4.3 When qualification has been granted, the PCD shall be signed by the supplier and Bombardier Aerospace Materials Technology Engineering and shall not be changed without prior written approval.

5.4.4 The PCD and all production data shall be available to Bombardier Aerospace auditors when requested.

5.5 Qualification Approval

5.5.1 Upon review of supplier's data, PCD and de Havilland tests, the supplier will be advised either of product qualification or reasons for not qualifying the product. Products that are qualified will be listed in the Qualified Products List of this specification.

5.5.2 No changes in the method of manufacture and/or formulation, shall be made without notification and prior written approval of Materials Technology Department.

de Havilland	DHMS: P 1.40
Material Specification	ISSUE: E
	AMD.: --
	DATE: August 2, 2016
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	PAGE: 14 of 19

- 5.5.3 Re-qualification of the product may be requested by the Bombardier Materials Technology if there are any changes in the method of manufacture and/or formulation.

6 QUALITY ASSURANCE REQUIREMENTS

6.1 Manufacturer/Supplier Batch/Lot Acceptance Tests

- 6.1.1 The manufacturer/supplier is responsible for the performance of all sampling, inspection and testing of each batch/lot as specified in [Table 5](#).
- 6.1.2 The manufacturer/supplier shall issue with each batch of product one copy of an Acceptance Test report showing actual test data conformance to the acceptance tests specified in [Table 5](#). The report shall include the supplier's batch identification, materials specification and date of testing.
- 6.1.3 Bombardier Aerospace Materials Technology Engineering reserves the right to perform any or all of the tests set forth in this specification to ensure that the product continues to meet specification requirements. Any product not meeting the requirements of this specification will be returned to the supplier at the supplier's expense.
- 6.1.4 The manufacturer/supplier shall certify with a Certificate Conformance that each batch of each shipment meets the requirements of this specification

6.2 Purchaser/User Batch/Lot acceptance tests

- 6.2.1 The purchaser/user is required to perform of all sampling, inspection and testing of each batch/lot as specified in [Table 5](#).

BOMBARDIER

de Havilland	Material Specification	DHMS: P 1.40 ISSUE: E AMD.: 1 DATE: April 21, 2017 PAGE: 15 of 19
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)		

TABLE 5. Qualification and Batch Acceptance Tests

Property	Requirement	Qualification (Manufacturer/ Supplier)	Acceptance	
			Manufacturer/ Supplier	Purchaser/User
Fabric Weight	Para.3.4.5	x	x	
Storage Life	Para.3.4.1	x		
Working Life	Para.3.4.2	x		
Formability	Para.3.4.3	x	x	
Volatile Content	Para.3.4.4	x	x	x
Resin Content	Para.3.4.5	x	x	x
Resin Flow	Para.3.4.6	x	x	x
Gel Time	Para.3.4.7	x	x	x
Tack	Para.3.4.8	x	x	x
Colour	Para.3.4.9	x		
Dimensions	Para.3.4.11	x		
Workmanship	Para.3.4.12	x	x	
Bias or Bowed Filling	Para.3.4.13	x		
Cure Cycle	Figure 4	x		
Flammability	Para.3.5.2	x	x	
Tensile Strength	Table 3	x		
Tensile Modulus	Table 3	x		
Flexural Strength at 75°F	Table 3	x	x	x
Flexural Strength at 300°F	Table 3	x		
Flexural Modulus	Table 3	x		
Compressive Strength	Table 3	x		
Horizontal Shear Strength	Table 3	x		
For acceptance test, condition at 70°± 5°F, 60% max relative humidity for a minimum of 24hrs. Test specimens at room temperature.				

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
		DATE: August 2, 2016
		PAGE: 16 of 19

6.3 Sampling

6.3.1 Sampling Schedule - Sampling shall be in accordance with [Table 6](#).

TABLE 6. Sampling Schedule

Number of Rolls in Batch	Frequency of Inspection
1 - 5	1 roll
6 - 15	1st and last rolls
16 and more	1st and every 10th and last rolls

6.3.2 Batch - A batch shall be all the product produced in a single production run from the same lot of raw materials under the same fixed conditions and submitted for inspection at one time. When more than one lot of aramid fibre fabric is used in production of a batch of prepreg to this specification, acceptance test shall be conducted so as to cover all lots of fabric batches utilized.

7 ORDERING DATA

7.1 Prerequisite

Material furnished under this specification for production use shall be qualified and listed on the Qualified Products List prior to issuing of a Purchase Order.

7.2 Procurement Documents

Procurement documents shall specify the following:

- Title, Number, Issue and Amendment Number of this Specification
- Type of Pre-Impregnated Fabric
- Manufacturer's Material Designation
- Total Quantity

8 PREPARATION FOR DELIVERY

8.1 Identification

8.1.1 Each roll of impregnated fabric shall be identified with a label or marking, securely affixed to the inside of the core or with a removable tag.

8.1.2 The label or removable tag shall use characters of a size such as to be clearly legible and which will not be obliterated by normal handling. Each label or tag shall show the following information:

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: --
	FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	DATE: August 2, 2016
		PAGE: 17 of 19

- Aramid Fiber Fabric, Epoxy Impregnated, 350° F Cure
- DHMS P1.40, latest Issue & Amendment
- Manufacturer's Material Designation
- Lot and Roll Numbers
- Quantity
- Perishable - Store Below 10°F
- Date of Manufacture

8.2 Packaging

- 8.2.1 The impregnated fiber shall be wound on spools not less than 3 inches in hub diameter and interleaved with a non-adherent film. The non-adherent film must be on the outside to prevent penetration of moisture or loss of impregnating resin solvent. The backing type shall be that is acceptable to Materials Technology.
- Winding shall be uniform and shall provide for proper unreeling. Fabric ends shall be secure.
- 8.2.2 Each roll shall be adequate support at both ends through the center of the core.
- 8.2.3 Each roll shall be sealed in a bag of suitable non-adherent material to prevent penetration of moisture or loss of impregnating resin solvent.
- 8.2.4 The roll shall be packed in an exterior shipping container capable of protecting the impregnated materials adequately at 10°F or lower during shipment and storage.

8.3 Shipping Documentation

- 8.3.1 Each shipping container shall have the exterior legibly marked with the following information in such a manner that the markings shall not smear or be obliterated during normal handling or use:
- Aramid Fiber Fabric, Epoxy Impregnated, 350° F Cure
 - DHMS P1.40, latest Issue & Amendment
 - Manufacturer's Material Designation
 - Purchase Order Number
 - Lot and Roll Numbers
 - Quantity
 - Perishable - Store Below 10°F
- 8.3.2 Containers shall be prepared for shipment in accordance with commercial practice to assure carrier acceptance and safe transportation to the point of delivery.
- 8.3.3 Each shipment shall contain a copy of the Material Safety Data Sheet.

de Havilland Material Specification	DHMS: P 1.40 ISSUE: E
FABRIC, ARAMID FIBER, HIGH MODULUS, 350°F CURE EPOXY RESIN IMPREGNATED (FOR INTERIOR USE)	AMD.: -- DATE: August 2, 2016 PAGE: 18 of 19

9 HEALTH AND SAFETY DATA

When supplying samples for qualification per [Para.5.2](#), the supplier shall submit a Material Safety Data Sheet (MSDS) complying with the "Controlled Products Regulations" of the Hazardous Products Act (also known as W.H.M.I.S. Regulations). The document must state all hazardous ingredients, safe-handling procedures, first-aid measures, fire and explosion data, reactivity data, physical properties, preparation information and procedures for storage and disposal.

This (MSDS) must then be supplied with a completed DH 4339 "Application To Introduce A New Material" form to the Material Safety Committee.

Upon receipt of DH 4340 "Recommendation" form that approves the use of the material, it can then be included on the Qualified Products List.

NOTE: Any changes in the formulation of the material require a re-submission of the Material Safety Data Sheet.

BOMBARDIER

de Havilland	Material Specification	DHMS: P 1.40
		ISSUE: E
		AMD.: 1
		DATE: April 21, 2017
		PAGE: 19 of 19

QUALIFIED PRODUCTS LIST

MANUFACTURER'S NAME AND ADDRESS	MANUFACTURER'S PRODUCT IDENTIFICATION NO.	DE HAVILLAND QUALIFICATION SHEET NO.	MSDS #	DATE OF PRODUCT APPROVAL
Cytec Solvay Group 501 West Third Street Winona, MN 55987	Type 3 L-756FR-285K Resin Flow 20-35% Gel Time 1-7 min.	PQS #5	2653	August 17, 2015